DEVELOPMENT OF LOW-TEMPERATURE FUSIBLE ENAMEL COMPOSITIONS BASED ON THE "KHIVA QUARTZ SAND – SULTAN UVAYS FELDSPAR – LEAD WASTE" SYSTEM

Buranova Dinara Baxtiyarovna

Urgench State University named after Abu Rayhan Biruni

Abstract. This article presents experimental research on the development of low-temperature fusible enamel frit compositions for glass surfaces, utilizing raw materials from the Khiva deposit feldspathic quartz sand, Sultan Uvays deposit feldspar, and lead-containing industrial waste. The developed compositions were tested in compliance with the requirements of state standards GOST 24405-80 and GOST R 52569-2018.

Keywords: glass enamel, frit, quartz sand, feldspar, lead waste, coefficient of linear thermal expansion (CLTE), visual quality, technological properties.

1. Introduction

The glass products manufacturing industry is one of the key sectors of the national economy worldwide. It consumes substantial amounts of raw materials, energy, and labor resources, which in turn determines the development level of the economy's core branches. Accordingly, the efficiency of the glass industry depends directly on the rational and economical use of these resources.

Rapid urban and industrial development has made metal structures among the most widely used materials in construction. Among these, enameled metal products based on iron are of particular importance. As petroleum prices continue to rise, the cost of corrosion-resistant materials derived from it also increases. Glass enamels have thus gained wide adoption as an alternative corrosion-resistant coating. Enameled metal surfaces offer advantages such as smoothness and durability, making them applicable not only in the construction sector but also in the food industry, pharmaceuticals, and other branches of the national economy.

Glass enamel samples were studied in accordance with the technical requirements of GOST R 52569-2018 (Frits. Technical Specifications) [1]. This research aims to make effective use of locally available raw material resources in Uzbekistan and to substitute imported products with domestically manufactured alternatives. In earlier studies [2–9], the authors investigated compositions of glass enamels for glass surfaces using Khiva deposit feldspathic quartz sands [11], Sultan Uvays deposit feldspar [12], lead-containing waste from zinc processing, and other local raw materials [13]. The influence of siliceous raw materials and alkaline earth metal oxides from the Khorezm region was examined in the course of these investigations.

2. Research Methods

The coefficient of linear thermal expansion (CLTE) of the glass enamel samples was determined by calculation, based on the methods specified in GOST R 52569-2018 and GOST 24405-80. The CLTE was calculated using the following formula:

$$\alpha = \Sigma\alpha_i \times m_i / 100 \quad (1)$$

where α_i is the coefficient of linear thermal expansion of the oxide or component in the frit composition over the temperature range of 20–400 °C ($°C^{-1}$); m_i is the molar fraction of each component (%).

Surface spreading of the samples was evaluated by selecting a standard enamel frit reference sample. Frit materials were placed on metal plates that had been washed with distilled water and dried, and the spreading lengths were measured before and after holding at 860 ± 5 °C for 15 minutes. The spreading value was calculated using the formula:

$$L = l_u / lCO \times la' \quad (2)$$

where l_u is the spreading length of the test frit sample (mm); lCO is the spreading length of the standard reference sample (mm); la' is the pre-determined spreading length of the standard reference sample (mm).

Chemical resistance of the samples to atmospheric conditions was assessed visually by monitoring changes upon exposure to drops of 10% citric acid solution. Surface microstructure was studied using a EM-5 electron microscope with the carbon plate technique. Microhardness was measured with a PMT-3 instrument at loads of 0.196 and 0.49 N [14].

3. Chemical Composition of Raw Materials

For developing the experimental glass frit compositions, Khiva deposit feldspathic quartz sand (HFQS), Sultan Uvays deposit feldspar (SUF), and lead waste (LW) were selected as primary raw material components (Table 1). Boron, titanium, and nickel oxides were added in chemically pure reagent form.

Table 1. Chemical composition of raw materials used for producing enamel coatings on glass surfaces

Sample name	SiO_2	Al_2O_3	Fe_2O_3	CaO	MgO	K_2O	Na_2O	PbO	ZnO	SO_3	LOI, wt.%
HFQS	97.04	1.25	0.10	0.21	0.10	0.13	0.40	–	–	–	0.77
SUF	74.08	13.64	0.05	0.55	0.30	9.01	1.56	–	–	–	0.60
LW	2.40	0.68	3.58	1.93	0.49	3.77	36.10	6.10	18.3	26.65	–

4. Development of Batch Compositions and Sample Preparation

Based on a review of the relevant literature, low-melting glass enamel compositions in the "quartz sand – feldspar – industrial waste" system were investigated. As a reference, the chemical composition (wt.%) prescribed by GOST 24405-80 for grade "ESG-31" (borate type) was adopted: SiO_2 – 45–52; Al_2O_3 – 5–7; Fe_2O_3 – <3; CaO – <7; Na_2O+K_2O – 16–20; B_2O_3 – 13–18; TiO_2 – <5; NiO – 0.5–3; CoO – 0.2–0.8.

Several compositions were prepared, and following comparative evaluation, three optimal batch compositions — GEF-1, GEF-2, and GEF-3 — were selected (Table 2).

Table 2. Batch compositions prepared for producing glass enamel from the studied raw materials (wt.%)

No.	Raw material	GEF-1	GEF-2	GEF-3
1	Khiva quartz sand	31.00	28.00	25.00
2	Sultan Uvays feldspar	29.00	29.00	29.00
3	Lead waste	6.00	8.00	10.00
4	Calcined soda	20.00	20.00	20.00
5	Boron oxide	14.00	15.00	16.00
Total (Σ, wt.%)		100	100	100

Na_2O was introduced into the glass batch through calcined soda. B_2O_3, TiO_2, and NiO were introduced as chemically pure reagents. TiO_2 and NiO were added at 5 wt.% and 2 wt.%, respectively, relative to the total mass. The resulting chemical composition of the developed enamel batches for glass surfaces is presented in Table 3.

Table 3. Chemical composition of the developed enamel batch compositions for glass surfaces

Sample	SiO_2	Al_2O_3	K_2O	Na_2O	CaO	MgO	Fe_2O_3	ZnO	PbO	B_2O_3	SO_3
GEF-1	51.74	4.45	2.70	12.11	0.37	0.17	0.27	0.37	2.17	13.72	1.10
GEF-2	48.88	4.43	2.69	12.18	0.41	0.18	0.34	0.49	2.89	14.70	1.46
GEF-3	46.02	4.41	2.69	12.24	0.44	0.19	0.41	0.61	3.61	15.68	1.83

5. Sample Preparation and Test Results

Each component was weighed out at 1 kg and glass enamel batch compositions were prepared according to the specified formulations. Samples were fused in unglazed corundum crucibles at 1200 °C with a 45-minute hold. The resulting glass melt was first quenched in a water bath at room temperature, then allowed to cool freely for 12 hours. The visual characteristics of the glass enamel samples are presented in Table 4 and Figure 1.

Table 4. Visual characteristics of the obtained glass enamel samples

Visual characteristics	GEF-1	GEF-2	GEF-3
Degree of fritting	Moderate	Good	High
Number of bubbles in fused glass, pcs. (per 1 cm^2)	7	4	None
Number of undissolved inclusions, pcs. (per 1 cm^2)	5	3	None

Visual inspection revealed that the sample produced from the GEF-3 experimental composition outperformed the others in terms of fritting degree and visual quality — no undissolved inclusions or bubbles were observed per 1 cm^2 of surface area (Figure 1).

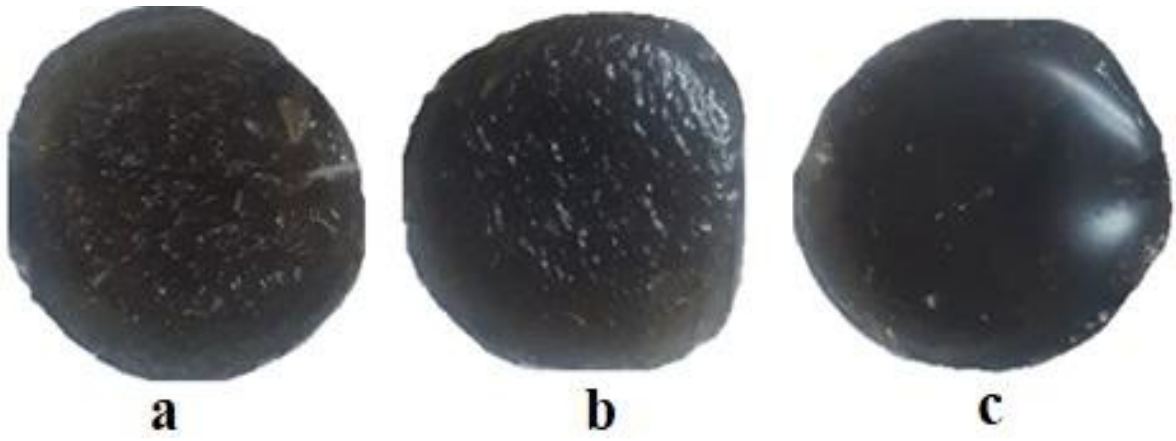


Figure 1. Visual appearance of glass enamel frit samples
a – GEF-1; b – GEF-2; c – GEF-3

To address the defects observed in GEF-1 and GEF-2, additional samples were prepared and compared at temperatures above 1200 °C and with firing durations ranging from 45 to 60 minutes. Based on the results, firing at 1200 °C for 45 minutes was identified as the optimal condition.

6. Technological and Physical Properties

The technological properties of the glass enamel frit samples for glass surfaces were determined in accordance with GOST 24405-80, and the results are summarized in Table 5.

Table 5. Technological properties of the obtained samples

No.	Technological property	GOST 24405-80	GEF-1	GEF-2	GEF-3
1	CLTE, $\alpha \cdot 10^{-7}$, $°C^{-1}$	95–105	91.5	94.2	97.4
2	Spreading on surface, mm	30–40	31	33	36
3	Adhesion strength, score	–	4	4	5

Analysis of the table shows that GEF-3 best satisfies the requirements of GOST 24405-80: CLTE of $97.4 \cdot 10^{-7}$ $°C^{-1}$, spreading of 36 mm, and an adhesion strength score of 5.

The key physical properties of the glass enamel frit samples were also determined, and the results are given in Table 6.

Table 6. Physical properties of the experimental glass enamel frit samples

Physical property	GEF-1	GEF-2	GEF-3
Density, g/cm^3	2.91	2.94	2.98
Refractive index	1.62	1.66	1.71
Softening temperature, °C	601	579	552
Mass loss in chemical medium, wt.%	0.26	0.27	0.27

7. Conclusions

Based on the results of the study, the following conclusions were drawn:

1. Three glass enamel frit compositions (GEF-1, GEF-2, GEF-3) were developed within the "Khiva quartz sand – Sultan Uvays feldspar – lead waste" system.

2. The GEF-3 composition (Khiva quartz sand 25 wt.%, Sultan Uvays feldspar 29 wt.%, lead waste 10 wt.%, calcined soda 20 wt.%, boron oxide 16 wt.%) fully complies with the requirements of GOST 24405-80.

3. No visual defects (bubbles or undissolved inclusions) were detected in GEF-3. The sample exhibited a CLTE of $97.4 \cdot 10^{-7}$ $°C^{-1}$, spreading of 36 mm, density of 2.98 g/cm^3, and a softening temperature of 552 °C.

4. The optimal firing condition was determined to be 1200 °C with a 45-minute hold.

References

1. GOST R 52569-2018. Frits. Technical Specifications. Moscow: Standartinform, 2018.
2. Buranova D.B., Babaev Z.K., Matchanov Sh.K., Karimov Sh.X., Kurbanova R.S. Glass formation with CaO, MgO and BaO in the system SiO_2-B_2O_3-Na_2O and their effect on some properties // International Journal of Bio-Science and Bio-Technology. Vol. 11, Issue 7, July 2019. – P. 166–172.
3. Buranova D.B., Yunusov M.Y., Babaev Z.K., Matchanov Sh.K., Matchanov Sh.Sh. On the use of cobalt-containing metallurgical waste to obtain colored glass and glass enamel // Journal of Glass and Ceramics, 2022. Vol. 79, Nos. 7–8. – P. 300–305.
4. Буранова Д.Б., Бабаев З.К., Матчанов Ш.К., Хакимова Г.Н., Хакимов М.С. Использование некоторых минеральных ресурсов Узбекистана в качестве мельничных добавок. Материалы Меж. нау. техн. конф. «Актуальные проблемы инновационных технологий в развитии химической, нефте-газовой и пищевой промышленности». Ташкент, 26-27 мая 2016. Часть I. – С. 296-297.

5. Буранова Д.Б., Бабаев З.К., Матчанов Ш.К., Курбанова Р.С. «Синтез легкоплавких стекол на основе минерального сырья Узбекистана для эмалирования стали» // Ж. UNIVERSUM: Технические науки. Москва. № 4(61) апрель, 2019.
6. Буранова Д.Б., Бабаев З.К., Матчанов Ш.К., Матчанов Ш.Ш. Ўзбекистонда шиша эмаллар ишлаб чиқаришни ташкил этиш ва уни ривожлантириш истиқболлари // Комплекс бирикмалар кимёси ва аналитик кимё фанларининг долзарб муаммолари" Респ. ил.- ама. конф. мат. тўп. 2-қисм.. Термиз 2022. 19-21 май. – Б. 338-339.
7. Буранова Д.Б., Бабаев З.К., Матчанов Ш.К., Аташев Э.А., Казаков У. Инновационная технология получение стекломозаичных плит // Кимё саноатида инновацион технологиялар ва уларни ривожлантириш истиқболлари. Респ. ил.- ама. конф. мат. тўп. Урганч, 2017. 1-жилд. – Б. 116-117.
8. Буранова Д.Б., Бабаев З.К., Матчанов Ш.К., Хаджиев А.Ш., Атаева Ф.А. Состав и лабораторная апробация получения стекловидной покрытий для майолики // Кимё саноатида инновацион технологиялар ва уларни ривожлантириш истиқболлари Респ. ил.- ама. конф. мат. тўп. Урганч. 2017. 1-жилд. – Б. 120-121.
9. Buranova D.B. Metall yuzalari uchun silikat emal olish texnologiyasi // Кимё саноатида инновацион технологиялар ва уларни ривожлантириш истиқболлари Респ. ил.- ама. конф. мат. тўп. Урганч. 2017. 1-жилд. – Б. 122-123.
10. Буранова Д.Б., Юнусов М.Ю., Бабаев З.К., Матчанов Ш.К., Искандаров О.Д. Стеклоэмалевые покрытия для эмалирования хозяйственно-кухонной посуды // "Kon-metallurgiya majmuasi: yutuqlar, muammolar va rivojlantirishning zamonaviy istiqbollari" IX xalqaro ilmiy-texnikaviy anjuman materiallari. Navoiy 12-14 iyun, 2017. – B. 468.
11. Buranova D.B. Main characteristics of quartz-feldspar sands from the Khiva deposit, and the physico-chemical and technological fundamentals of obtaining an enriched concentrate. Kompleksnoe Ispolzovanie Mineralnogo Syra = Complex Use of Mineral Resources. 2027; 340(1): 37–44. https://doi.org/10.31643/2027/6445.04
12. Buranova D., Matchanov Sh., Atashev E. Physicochemical and mineralogical characterization of Sultan Uwais feldspar for sustainable glass manufacturing in earth and environmental sciences. E3S Web of Conferences 633, 06001 (2025). https://doi.org/10.1051/e3sconf/202563306001
13. Buranova D.B., Atashev E.A., Matchanov Sh.K., Kurambaev Sh.R. Opportunities to Obtain Glass Enamel Frits Based on the Raw Materials of the Lower Amudarya Region // In Proceedings of the 6th International Conference on Construction Mechanics, Hydraulics and Water Resources Engineering Autumn Season (CONMECHYDRO 2024). DOI: 10.5220/0013533100004644. P. 253–258. ISBN: 978-989-758-768-9; ISSN: 3051-7095.
14. GOST 24405-80. Silicate Enamels (Frits). Technical Specifications. Moscow, 1980.